

ConCrib



Shear resistance test
Flashjoint
200 mm

ConCribes



Reference	KF20210518
Project name	SHEAR TEST FLASH JOINT 200 MM
Date	2020.03.24
Contact	TOFTEGAARD BYG
Designed by	ABO
Verified by	AFO
Customer name	TOFTEGAARD BYG / FLASH JOINT

Scope

The purpose of the test is to document the shear resistance of flashjoint 200 mm in a concrete joint in a 200 mm thick concrete beam.


The test is designed as beams of 400 mm length and 100 mm width, with thickness 200 mm to be tested according to EN 12504-3 for pull off resistance.

The beams are produced at a precast plant using C20/25 concrete to demonstrate the lowest possible performance at low concrete grade. Concrete is certified to EN 206.

ConCribе




The flashjoints to be poured at the center of the test beams per the following drawing:

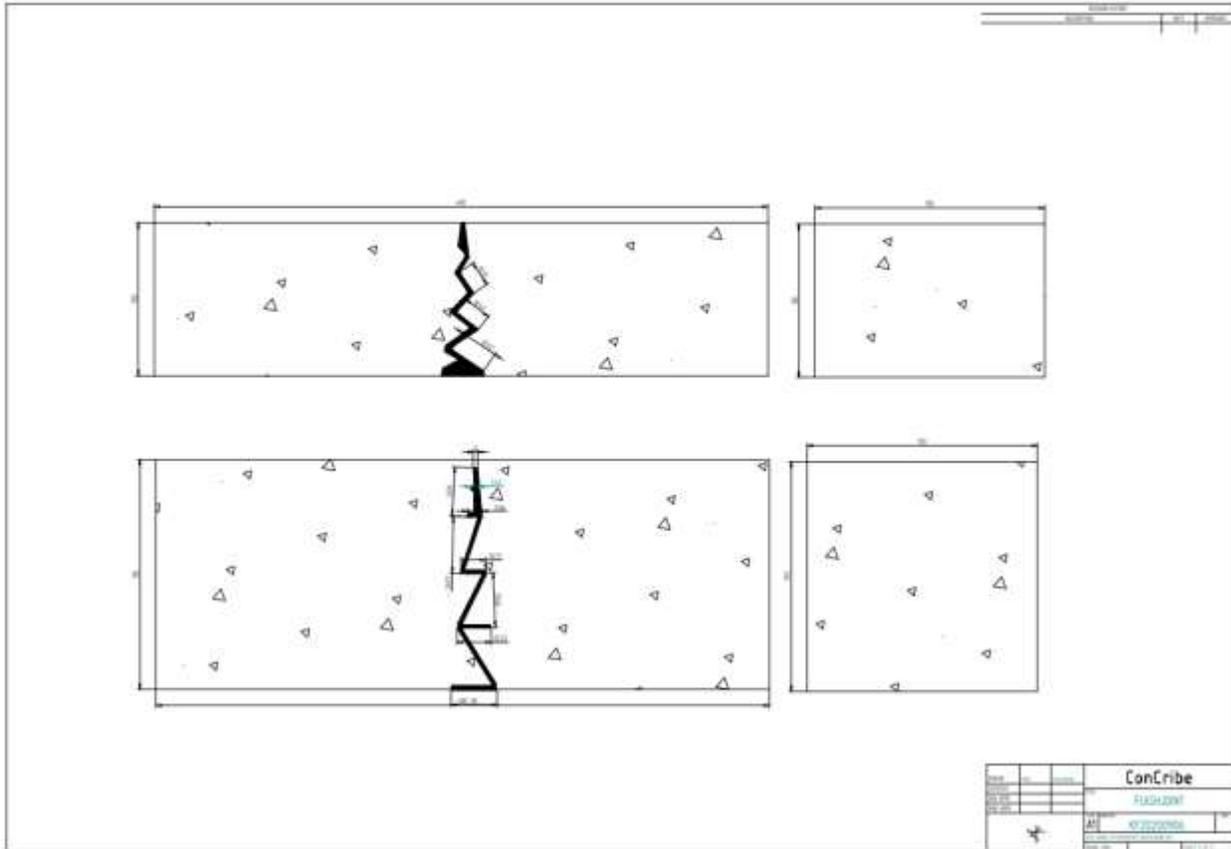

Design of the test beams and location of the flashjoint 100 and 150.

NOTE: THICKNESS OF THE CONCRETE BEAMS IS 100 MM INSTEAD OF 150 MM

ConCrib

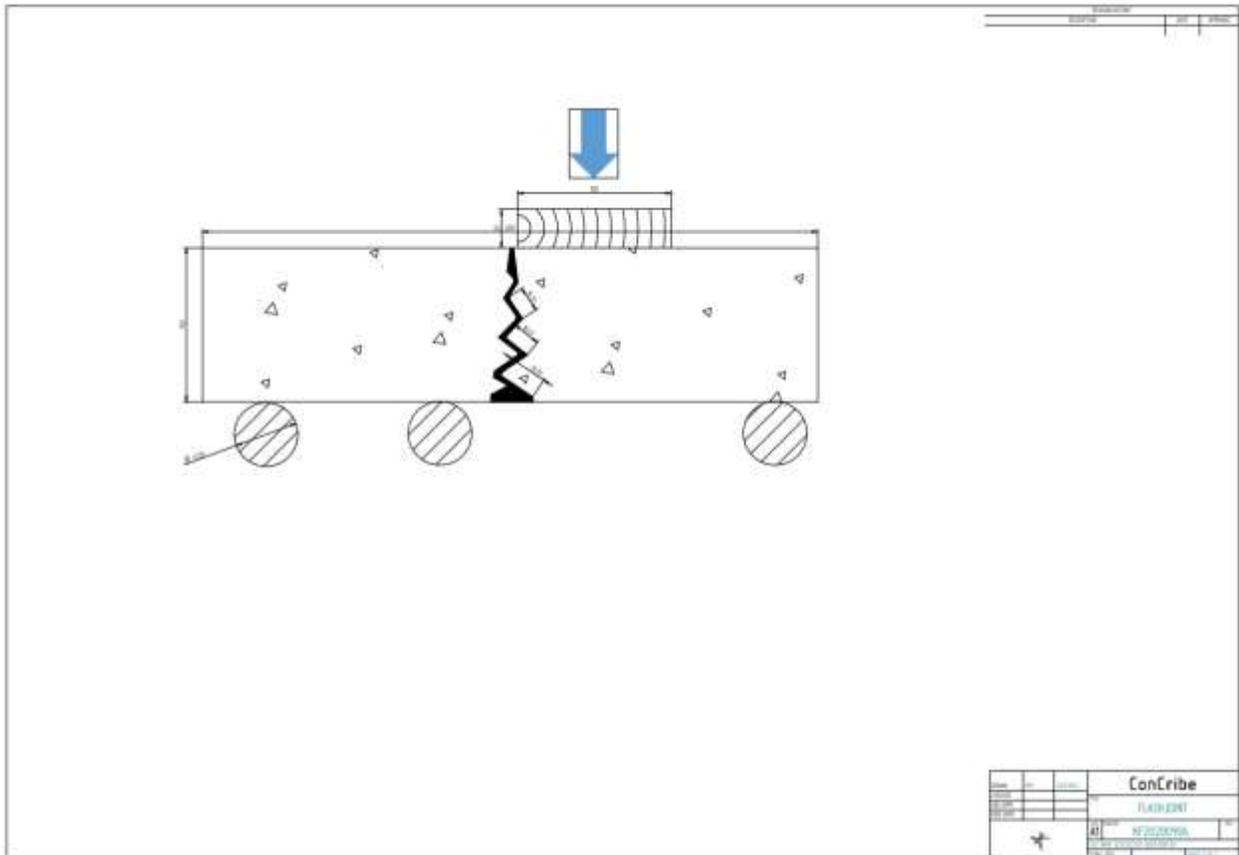

Test set up

Each beam is placed one at a time on the test bench against the above test sketch. One part of the beam across the flashjoint is fully supported along its length so movement in y direction is restrained entirely. The other part is only supported at end so it's free to move in y direction when pressure on this part close to the joint increases.

ConCribes



Test equipment

20 tons bench with hydraulic indicator



The bench is certified to :

Directive/Regulation	Harmonised standard
2006/42/EC	EN 1494:2000+A1:2008 EN ISO 12100:2010 EN ISO 13857:2008 EN 349:1993+A1:2008

ConCribes



Test set up

Beams

The beams were poured on 23-04-21, 24-04-21 and 25-04-21
They were demolded at 12 hours and stocked into 20 degrees hot water for 20 days.
Test was performed on 17-05-2021

Test report

FJ200 23-4-21



ConCrib



No First crack
Collapse at 4 tons

ConCribes



FJ100 24-3-21



ConCribes



No First crack
Collapse at 4.5 tons

ConCrib



FJ200 23-4-21



No First crack
Collapse at 4.5 tons

ConCribes



Test conclusions

Ø	Diameter of the cylinder	45 mm
A	Area cylinder	1590 mm ²
Ac	concrete section area	20000 mm ² (100 x 200 mm)
P ₀	Pressure at first crack	
P ₁	Pressure at collapse	
F ₀	Force at first crack Mpa	
F ₁	Force at collapse Mpa	
R ₀	Shear resistance Mpa	
R ₁	Shear resistance Mpa	
R _s	Shear resistance at SLS of FJ 200 per meter	
R _u	Shear resistance at ULS of FJ 200 per meter	
V _c	shear capacity concrete	V _c =0.34 Mpa for 30 Mpa concrete.

FJ 200	P ₀ t	P ₁ t	F ₀ Mpa	F ₁ Mpa	R ₀ Mpa	R ₁ Mpa	R _s kN/m	R _u kN/m
23-avr	0	4	0	1,24	0	0,90	0	180
24-avr	0	4,5	0	1,40	0	1,06	0	211
25-avr	0	4,5	0	1,40	0	1,06	0	211
Average								201

Test expectations


Flashjoint	LTE
200	100 % up to 41 kN/m

ConCribes



Model without FJ

Thickness	200 mm	
Subgrade	5 N/cm ³ *	*min. value
HGV	44 t – wheel load 25 kN unfactored **	** assumed

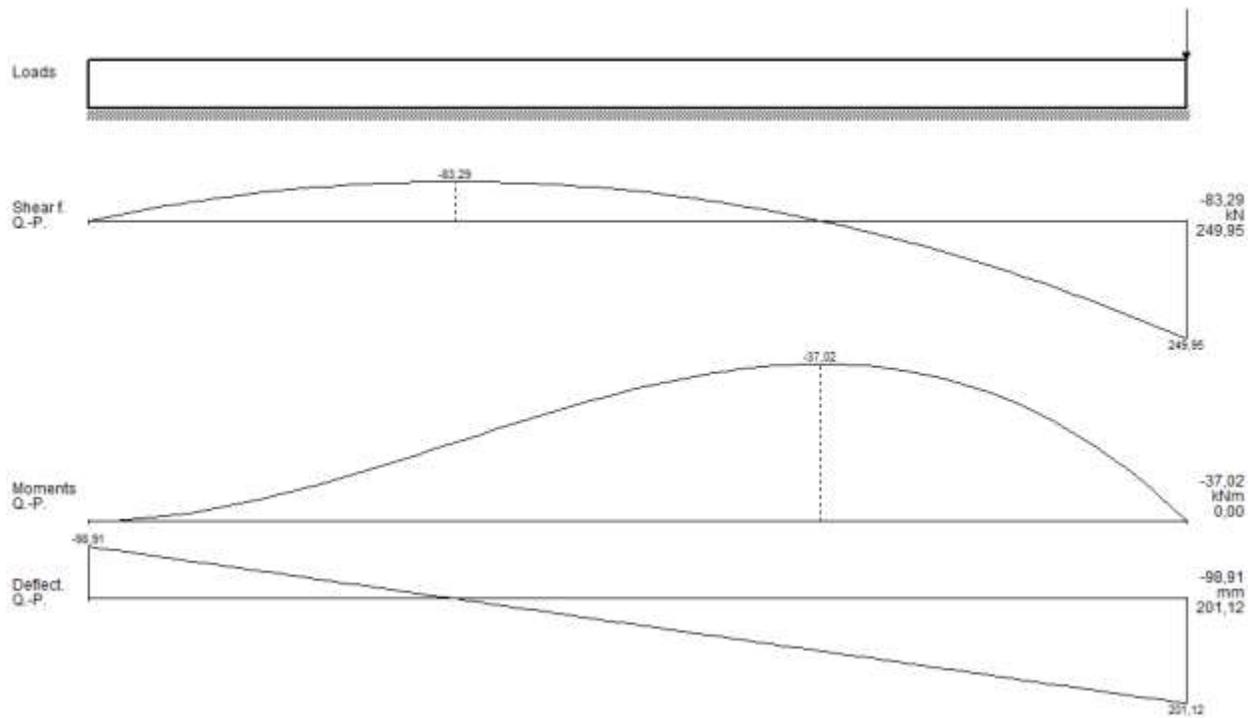

Shear force in the joint : 250 kN/m

ConCribes




Model with FJ

Thickness 200 mm
 Subgrade 5 N/cm³*
 HGV 44 t – wheel load 25 kN unfactored **
 Elastic support (FJ) 41 kN/m

*min. value

** assumed

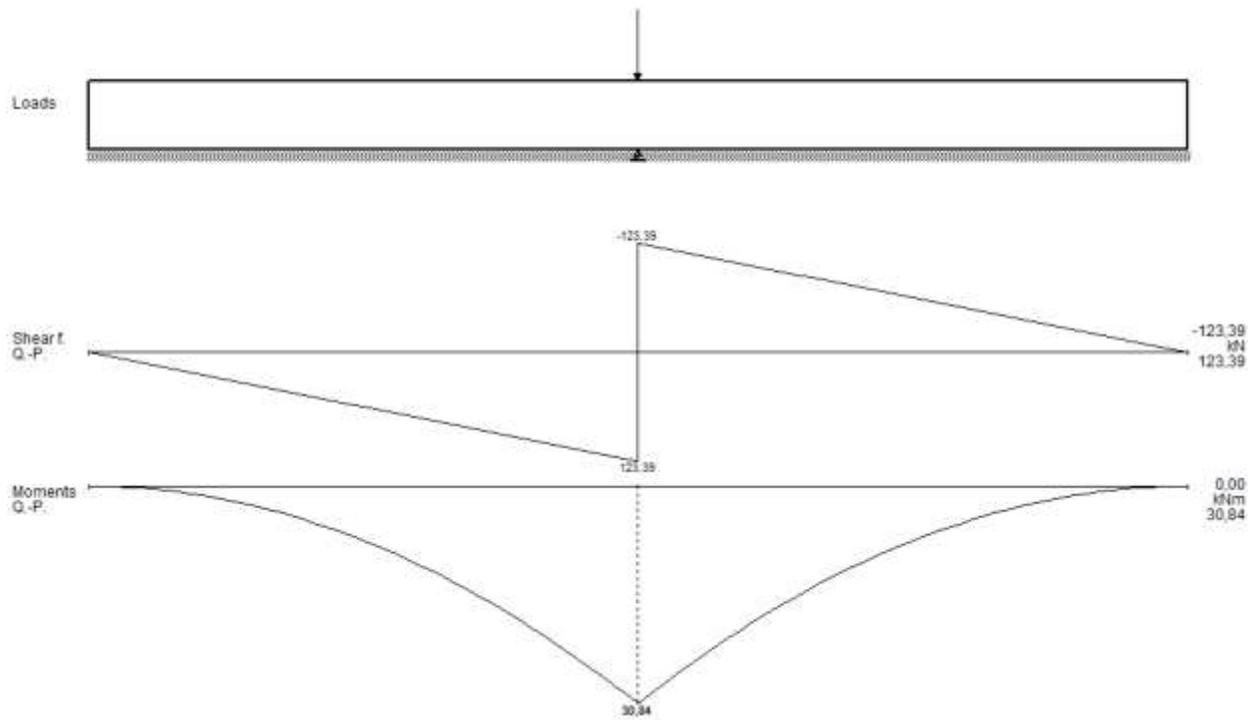

Conclusion model

FJ 150	Without FJ kN/m	With FJ kN/m	Value of shear resistance FJ
Shear	250 kN/m	123.4	126.6 kN/m

ConCrib



Test conclusion

The tested shear resistance of Flashjoint 200 has shown **201 kN/m at SLS**. It is to be noted that the beam was NOT supported as it was calculated to be in the expected test calculation.

The modelled test resistance has shown **126 kN/m** for a 44 t HGV on 3 axles at SLS.

Since CS TR₃₄ does consider the use of dowels to reduce load transfer by 30 %, the use of FlashJoint is indeed a valid alternative to dowels and bars, as it conservatively reduces load transfer with **50 % (250/126)**

Test was performed with plain concrete, FRC would improve results in any case.